

Synthesis and Characterization of Silver Nanoparticles from *Ocimum basilicum L. var. thyrsoiflorum*

Anuradha.G¹, B. Syama Sundar*¹, J. Sreekanth kumar²,
M.V. Ramana³

¹Department of Chemistry, Acharya Nagarjuna University, Guntur, A. P. India.
anuradha.mythri@gmail.com

*Present position: Vice- Chancellor, Yogi Vemana University, Kadapa, A. P. India.
profbsyamsundar@yahoo.co.in

²Department of H&S, Swarna Bharathi Institute of Science and Technology, Khammam, A. P. India.
Sreekanth.mythri@gmail.com

³Department of Physics, SR&BGNR Govt. Arts & Science College, Khammam, A. P. India.
mvr1508@gmail.com

Abstract: Biosynthesis of nanoparticles is an important area in the field of nanotechnology, which has economic and eco-friendly benefits over chemical and physical methods of synthesis. In the present study leaf extract of *Ocimum basilicum L. var. thyrsoiflorum* was assessed for the synthesis of Silver nanoparticles using 1mM Silver Nitrate aqueous solution. Nanoparticles were characterized with the help of UV-Vis absorption spectroscopy analysis, Fourier Transform Infrared (FTIR) analysis, Scanning Electron Microscopy (SEM) and EDX analysis. The Synthesized nanoscale particles were confirmed by analyzing the excitation of Surface Plasmon Resonance (SPR) using UV-visible spectrophotometer at 436nm. Further SEM analysis confirmed the range of particle size between 22 to 42 nm. Fourier transform infrared spectrum confirmed the presence of high amount of phenolic compounds in the plant extract, possibly influenced the reduction process and stabilization of nanoparticles.

Keywords: Silver nanoparticles, Surface Plasmon Resonance, *Ocimum basilicum L. var. thyrsoiflorum*, Silver Nitrate, SEM analysis.

1. Introduction

Nanotechnology is an active area of research with tremendous applications for society, industry and medicine. The non-polluting nanotechnologies have revolutionized the production of nanomaterials as environmentally safe products. Several chemicals used in the chemical and physical synthesis of nanoparticles are toxic which leads to environmental pollution [1]. Therefore biological sources can be an alternative for the synthesis of nanoparticles [2]-[4]. Plants are the richest bioresources of drugs in traditional and modern medicine [5]. Silver nanoparticles have wide range of applications such as catalysis [6], drug delivery [7], biosensing [8], [9] and optics [10]. Biogenic path of nanoparticle synthesis using microorganisms [11]-[13], enzymes [14] and plant extracts [15]-[20] were suggested as possible ecofriendly alternatives to chemical and physical methods. Here we report an in expensive and green method for the synthesis of Silver nanoparticles by reduction process

using *Ocimum basilicum L. var. thyrsoiflorum*, the plant is extensively used in traditional medicine. The genus *Ocimum*

belongs to Lamiaceae family and consists of 160 species with 24 species native to India [21]. The essential oils of *Ocimum* consists eugenol, methyl chavicol, linalool, geraniol, 1,8-cineol, citral and camphor [22]. These essential oils are being used as pharmaceutical agents because of their anticancer, antiasthmatic, antistress, antimicrobial activity [23], antidiabetic [24] and antioxidant activity [25]. Herein we report the Synthesis and characterization of Silver nanoparticles first time from *Ocimum basilicum L. var. thyrsoiflorum*.

2. Materials and Methods

2.1 Collection of plant material

The genus *Ocimum* belongs to Lamiaceae family. *Ocimum basilicum L. var. thyrsoiflorum* (Fig. 1) is a traditional medicinal plant distributed in most parts of the India. Local name is Adavi sabza or Tella sabza and the trade name is

Basil. The plant is stout, nearly glabrous and herbaceous with short recemes. Leaves are elliptic and ovate and the flowers are white in terminal thyrsoid panicles (Fig. 2).

Ocimum basilicum L. var.thyrsoiflorum leaves were collected from the Medicinal plant garden, SR&BGNR Govt. Arts & Science College of Khammam, Andhra Pradesh and identified by the plant systemic laboratory, Department of Botany, Kakatiya University, Warangal, A.P.India and further the voucher specimen was preserved in the department as a record.



Figure 1: *Ocimum basilicum L. var.thyrsoiflorum* plant



Figure 2: Inflorescence.

2.2 Preparation of leaf extract

Fresh basil leaves were washed several times with tap water and later with deionised water. 10 grams of washed fine cut leaves along with 100 ml double distilled water were taken in 250 ml glass beaker and boiled for 5 minutes at 80°C. The extract was cooled to room temperature and filtered with Whatman No 1 filter paper. The filtrate was centrifuged for 10 minutes at 10000 rpm, the supernatant was collected and stored at 4° C. The filtrates are used as reducing and stabilizing agents.

2.3 Preparation of 1 mM AgNO₃ solution

Accurate concentration of 1 mM AgNO₃ (Merck India Ltd) was prepared by dissolving 0.169 gm AgNO₃ in 1000 ml double distilled water and stored in Amber coloured bottle to avoid auto oxidation of Silver.

2.4 Bio synthesis of Silver nanoparticles

In the single step green synthesis, 5 ml of leaf extract was added to 95 ml of 1 mM aqueous AgNO₃ solution and heated up to 80°C for 5 minutes, the immediate colour change (Fig. 3) indicate the formation of Silver nanoparticles.



Figure 3: *Ocimum basilicum L. var.thyrsoiflorum* leaf extract, aqueous AgNO₃, Silver nano particles and color change respectively.

The silver nanoparticles solution thus obtained was purified by repeated centrifugation at 10000 rpm for 15 minutes. The supernatant was transferred to a clean dry beaker for further settlement of particles and repeated centrifugation was carried using cooling microfuge to get dried and purified Silver nanoparticles. The particles obtained were used for further characterization.

3. Characterization

3.1. UV –Visible spectra analysis

Synthesized silver nanoparticles were initially characterized by taking small aliquot of sample in to UV –Visible spectrophotometer absorption spectra at 300-700 nm using Shimadzu UV -1800 Spectrophotometer.

3.2. SEM analysis of silver nanoparticles

Scanning electron microscopic (SEM) analysis was carried by using Zeiss, EV-18 model.

3.3 EDX Analysis

Energy Dispersive X-ray analysis (EDX) was carried out on Zeiss, EV-18 model. The peaks obtained from EDX gives the element composition of the sample.

3.4 FTIR- Spectroscopy

Fourier-transform infra red spectroscopy Bruker Tensor 27 model was used for the analysis of the reduced silver. The spectrum was recorded in mid-IR region of 400-4000 cm⁻¹ with 16 scan speed, using attenuated total reflectance (ATR) technique.

3.5 Preliminary screening of Phytochemicals

About 10 gram of washed fine cut leaves were soaked in 100 ml of deionised water and boiled for 5 minutes to obtain crude extract. Harborne, 1998 method was employed to screen the phytochemicals present in the leaf extract [26]. Natural chemical groups such as amino acids, proteins, carbohydrates, flavonoids, sterols, terpenoids and phenolic compounds were identified and reported in Table No.1. The aqueous extract was further exemplified by FT-IR spectroscopic studies to reveal the presence of characteristic functional groups.

Table No.1 Preliminary Screening of Phytochemicals (+) presence (-) absence

S.No	Phytochemicals	Result
1.	Amino acids	+
2.	Carbohydrates	+
3.	Alkaloids	-
4.	Flavonoids	+
5.	Saponins	-
6.	Sterols	+
7.	Tannins	-
8.	Proteins	+
9.	Phenolic compounds	+

4. Results and Discussion

The present study reports the use of *Ocimum basilicum L. var.thrysiflorum* for the Synthesis of Silver nanoparticles. The plant extract may act as reducing and capping agents in silver nanoparticles synthesis. Studies have indicated that biomolecules like protein, carbohydrates, flavonoids and phenols not only play a role in the capping of the nanoparticles, but also play an important role in reducing the ions to the nano size [27], [28]. The biomolecules found in these extracts like enzymes, vitamins, proteins, amino acids, and polysaccharides [29] play a vital role in the reduction of Ag⁺ ions.

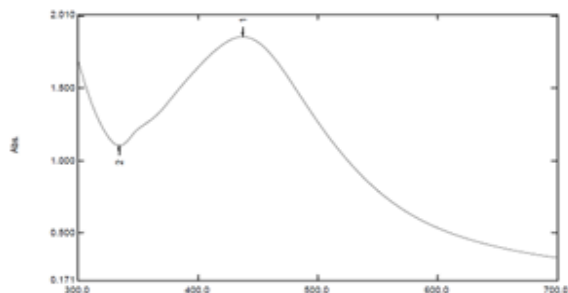


Figure 4: UV-Visible absorption spectrum of *Ocimum basilicum L. var.thrysiflorum*

The nanoparticles were primarily characterized by UV-Visible Spectroscopy, which is proved to be a very useful technique for the analysis of nanoparticles. As the leaf extract was mixed with the aqueous solution of the silver ion complex it was changed from red to golden yellow colour (Figure 3). This is due to the excitation of the surface plasma vibrations, which indicates the formation of the Silver nanoparticles [30]. UV-Visible Spectrograph of Silver nanoparticles has been recorded as a function of time by using quartz cuvette with distilled water as the reference. The UV spectrum absorption is recorded at 436 nm (Fig. 4).

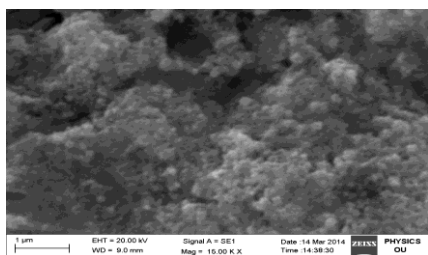


Figure 5: SEM image of silver nanoparticles formed by *Ocimum basilicum L. var.thrysiflorum*

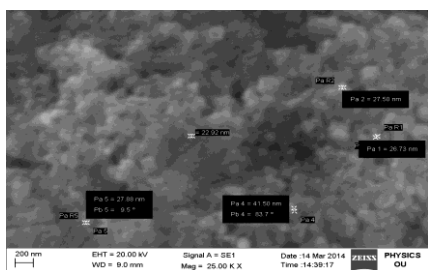


Figure 6: SEM image showing the size of silver nanoparticles.

The SEM image (Fig. 5) is showing the high density silver nanoparticles synthesized from the leaf extract, further confirmed the development of silver nano structure. The SEM image shows the formation of porous surface with spherical nano particles. They are clearly distinguishable in 22.92-41.50 nm in size (Fig. 6).

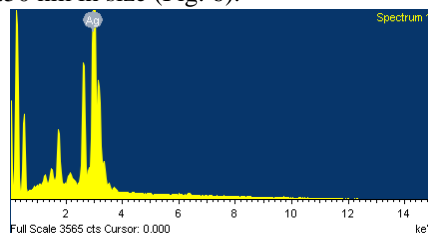


Figure 7: EDX image of silver nanoparticles produced from *Ocimum basilicum L. var.thrysiflorum*.

The EDX spectra exhibit the purity of the material and the complete chemical composition of synthesized silver nanoparticles. In the present synthesis EDX analysis (Figure.7) shows high percentage of silver indicating the purity of the synthesized sample.

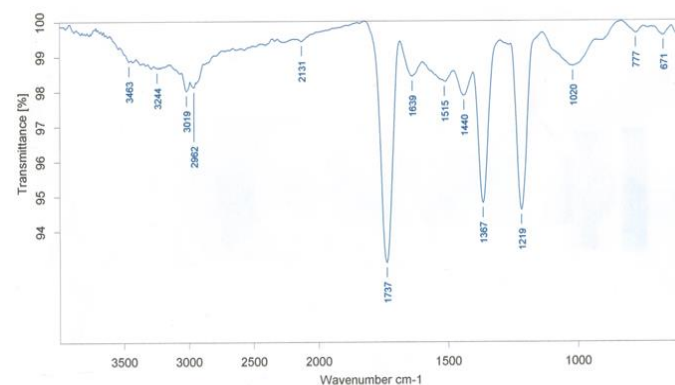


Figure 8: FTIR-spectrum of bio synthesized silver nanoparticles formed by *Ocimum basilicum L. var.thrysiflorum*.

The FTIR spectrum of silver nanoparticles is shown in Figure.8. The band at 3463cm⁻¹ is assigned to the O-H stretching of H-bonded alcohols and phenols. The peak formed at 2962 cm⁻¹ is because of C-H stretching and symmetric stretching of methoxy groups. The strong peak at 1737 cm⁻¹ shows the stretching vibrations of C=O. The band at 1639 cm⁻¹ corresponds to the N-H bending of primary amines. The value 1440 cm⁻¹ is related to the C-C stretching of aromatic ring structure. The bands at 1367cm⁻¹ are related to the C-N stretching of aromatic amine group. Whereas in the region 1020 cm⁻¹ are corresponding to the C-C stretching of alcohols, carboxylic acids, ethers and esters which are binding to metal to form a silver nanoparticle.

The preliminary phytochemical analysis of leaf extract revealed the presence of amino acids, carbohydrates, flavonoids, sterols, terpenoids, proteins, and phenolic compounds as shown in Table.1. FT-IR predicts the molecular configuration of different functional groups present in the extract. Considerable absorption peaks are found at 3463cm⁻¹, 2962 cm⁻¹, 1737 cm⁻¹, 1639 cm⁻¹, 1440 cm⁻¹, 1367cm⁻¹, 1020 cm⁻¹ respectively (Fig. 8). In the present study ,the peaks are more charecteristic of eugenol [32],linalool, methylchavicol and flavanoids.

5. Conclusion

The present study reveals that the plant species of *Ocimum basilicum L. var. thrysiflorum* is good source for the synthesis of silver nanoparticles at a faster rate. The formation of silver nanoparticles was confirmed by the colour change within 30 minutes. The bioreduced silver nanoparticles were characterized using UV-Vis, SEM, FTIR techniques.

The Silver nanoparticles formed were quite stable in the solution. SEM analysis confirmed the range of particle size between 22 to 42 nm. The carbohydrates, flavanoids and poly phenols constituents present in leaf extract act as the surface active stabilizing molecules for the synthesis of Silver nanoparticles. The method was unique and cost effective. Still more clinical trials are needed to support its therapeutic uses.

Acknowledgements

The authors gratefully thank the Department of Physics, Osmania University, Hyderabad for SEM, EDX and spectral analysis. The authors are thankful to Prof. Vatsavaya S. Raju, Plant Systematic Laboratory, Department of Botany Kakatiya University, Warangal, A.P.India for the identification of plant species.

References:

- [1] Esumi K, Kameo A, Suzuki A, Torigoe K. "Preparation of gold nanoparticles in formamide and N,N-dimethylformamide in the presence of poly(amidoamine) dendrimers with surface methyl ester groups". *Colloids and Surf A: Physicochem. Eng. Aspects.* 189(1-3), pp. 155-161, 2001.
- [2] Prathna TC, Mathew L, Chandrasekaran N, Raichur AM, Mukherjee A. "Biomimetic Synthesis of Nanoparticles: Science, Technology & Applicability", Edited A. Mukherjee, InTech Publishers, Croatia, pp. 1-20, 2010.
- [3] Singaravelu G, Arockiamary JS, Ganesh Kumar V, Govindaraju K. "A novel extracellular synthesis of monodisperse gold nanoparticles using marine alga, *Sargassum wightii* Greville". *Colloids Surf .B Biointerfaces.* 57, pp. 97-101, 2007.
- [4] Mubarak Ali D, Sasikala M, Gunasekaran M, Thajuddin. "Biosynthesis and Characterization of silver nanoparticles using marine cyanobacterium, *Oscillatoria willei* NTDM01". *Dig. J.Nanomater. Bios.* 6(2), pp. 385-390, 2011.
- [5] U.Viplav Prasad, B Syama sunder G.Anuradha, J.Sreekanth kumar "Chemical examination of *Morinda pubescens* Ver. *pubescens* and Isolation of crystalline constituents" *Proceedings of Chemistry of Phytopotentials: Health,Energy & Environmental Perspective*, pp. 73 – 76, 2011.
- [6] Tsang, C, Caps, V, Paraskevas, I, Chadwick, D, Thompsett, D: "Magnetically separable, carbon-supported nanocrystals for the manufacture of fine chemical". *Angew Chem* 116, pp. 5763–5767, 2004.
- [7] Baptista, PV: "Cancer nanotechnology - prospects for cancer diagnostics and therapy". *Curr Canc Ther Rev* 5(2), pp. 80–88, 2009.
- [8] Huang, CC, Yang, Z, Lee, KH, Chang, HT: "Synthesis of highly fluorescent gold nanoparticles for sensing mercury (II)". *Angew Chem Int Ed* 46, pp.6824–6828, 2007.
- [9] Jain, PK, Lee, KS, El-Sayed, IH, El-Sayed, MA: "Calculated absorption and scattering properties of gold nanoparticles of different size, shape, and composition: applications in biological imaging and biomedicine". *J Phys Chem B* 110, pp. 7238–7248, 2006.
- [10] Murphy, CJ, Sau, TK, Gole, AM, Orendorff, CJ, Gao, J, Gou, L, Hunyadi, SE, Li, T: "Anisotropic metal nanoparticles: synthesis, assembly, and optical applications". *J Phys Chem B* 109, pp.13857–13870, 2005.
- [11] T. Klaus, R. Joerger, E. Olsson, and C. G. Granqvist, "Silver based crystalline nanoparticles, microbially fabricated," *Proceedings of the National Academy of Sciences of the United States of America*, 96, (24), pp. 13611–13614, 1999.
- [12] Y. Konishi, K. Ohno, N. Saitoh et al., "Bioreductive deposition of platinum nanoparticles on the bacterium *Shewanella algae*," *Journal of Biotechnology*, 128(3), pp. 648–653, 2007.
- [13] B. Nair and T. Pradeep, "Coalescence of nanoclusters and formation of submicron crystallites assisted by *Lactobacillus* ," *Crystal Growth and Design*, 2(4), pp. 293–298, 2002.
- [14] I.Willner, R. Baron, and B.Willner, "Growing metal nanoparticles by enzymes," *Advanced Materials*, 18(9), pp.1109–1120, 2006.
- [15] Kumar V,Yadav SK. "Pant mediated synthesis of silver and gold nanoparticles and their applications", *J.Chem Technol Biotechnol*;(84), pp.151-157, 2009.
- [16] Vyom parashar*,et al, "Parthenium leaf extract mediated synthesis of silver nanoparticles: a novel approach towards weed utilization". *Digest Journal of Nanomaterials and Biostructures .* 4,(1), pp. 45 - 50, 2009.
- [17] Gnanasekar Sathishkumara , Chandrakasan Gobinatha , etal., "Phyto-synthesis of silver nanoscale particles using *Morinda citrifolia L.* and its inhibitory activity against human pathogens". *Colloids and Surfaces B: Biointerfaces* (95), pp. 235– 240, 2012.
- [18] Yogeswari Rout, Sikha Behera, Akshya Kumar Ojha and P. L. Nayak* "Green synthesis of silver nanoparticles using *Ocimum sanctum* (Tulashi) and study of their antibacterial and antifungal activities". *J. Microbiol. Antimicrob.*Vol. 4(6), pp. 103-109, 2012.
- [19] Ponarulselvam S, Panneerselvam, Murugan K, Aarthi N, Kalimuthu K, Thangamani., "Synthesis of silver nanoparticles using leaves of *Catharanthus roseus* Linn. G. Don and their antiplasmodial activities" ,*Asian Pacific Journal of Tropical Biomedicine* , pp.574-580, 2012.
- [20] Chidambaram Jayaseelan, et al, "Acaricidal efficacy of synthesized silver nanoparticles using aqueous leaf extract of *Ocimum canum* against *Hyalomma anatolicum anatolicum* and *Hyalomma marginatum isaaci*(Acari:Ixodidae)" *Parasitology research*, 11(3), pp.1369-78, 2012.
- [21] Gupta R. etal, "Basil(*Ocimum spp.*)G-15 Gene Banks for medicinal and aromatic plants". *NewsLetter*, 1, pp. 1-3, 1994.
- [22] M. Tamil Selvi, et al, "Antioxidant and cytotoxic activities of essential oil of *Ocimum canum* Sims. from India". *Journal of Saudi Chemical Society*, pp.1-4, 2012.
- [23] Jeferson c. Nascimento ,et al, "Chemical composition and antimicrobial activity of essential oils of *ocimum canum* sims. and *ocimum selloi* benth". *Anais da Academia Brasileira de ciencias* 83(3), pp. 787-799, 2011.

- [24] Nyarko A.K. et al, "Extract of *Ocimum canum* lowers blood glucose and facilitates insulin release by isolated pancreatic beta-islet cells". *Phytomedicine*, 9(4) pp. 346-351, 2002.
- [25] Behera Saiprasanna, et al, "Phytochemical investigation and study on antioxidant properties of *Ocimum canum* hydro-alcoholic leaf extracts". *Journal of Drug Delivery & Therapeutics*; 2(4), pp.122-128, 2012.
- [26] Harborne JB, "Phytochemical methods—A guide to modern techniques of plant analysis", Chapman and Hall Ltd, London, 1998.
- [27] A. Vedpriya, "Living Systems: eco-friendly nanofactories," *Digest Journal of Nanomaterials and Biostructures*, 5(1), pp. 9–21, 2010.
- [28] O. Collera-Z uñiga, F. Garc'ia Jim'enez, and R. Mel'endez Gordillo, "Comparative study of carotenoid composition in three mexican varieties of *Capsicum annum* L.," *Food Chemistry*, 90, (1-2), pp. 109–114, 2005.
- [29] B. H. Jagadeesh, T. N. Prabha, and K. Srinivasan, "Improved shelf life of bell capsicum fruits by manipulation of the activities of glycosidases through heat," *Indian Journal of Plant Physiology*, 9(2), pp. 164–168, 2004.
- [30] S. S. Shankar, A. Rai, B. Ankamwar, A. Singh, A. Ahmad, and M. Sastry, "Biological synthesis of triangular gold nanoprisms", *Nature Materials*. 3, pp. 482–488, 2004.
- [31] Sapna Phadtare, Rahul Pandit, Vaibhav Shinde, Kakasaheb Mahadik, "Comparative Phytochemical and Pharmacological Evaluations of Two Varieties of *Ocimum basilicum* for Antiarthritic Activity", *J. of Pharmacognosy and Phytochemistry* , 2 (2), pp. 158-167, 2013.

Author Profile



Anuradha.G received B.Sc., degree in Biochemistry from Kakatiya University in 1999 and M.Sc., degree in Medicinal chemistry from Osmania University in 2001. She received M.Phil degree from Acharya Nagarjuna University, A.P, India, in 2006 and presently in pursuit of Ph.D., from the same university.